

Test Report

SL52505272948001TX

Date: February 27, 2025 Page 1 of 4

WIPECO INDUSTRIES INC
MONTREAL 3333 DOUGLAS B FLOREANI MONTREAL QC CA H4S 1Y6

The following sample(s) was/were submitted and identified on behalf of the client as:

Sample Description : (A) Microporous disposable coverall

Sample Color : (A) White

Composition : (A) Non woven composite breathable film

Style No. : CMP50127W

Proposed Care Instruction : -


Test Performed : Selected test(s) as requested by applicant

Sample Receiving Date : Feb 19, 2025

Testing Period : Feb 20, 2025 - Feb 27, 2025

Test Result(s) : Unless otherwise stated the results shown in this test report refer only to the sample(s) tested, for further details, please refer to the following page(s).

Signed for and on behalf of
SGS-CSTC Standards Technical Services (Shanghai) Co., Ltd

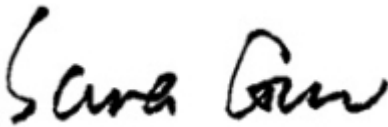

Sara Guo (Account Executive)

SGS does not verify authenticity of any Brand/Trademark of products. Buyers must check if the product is genuine with the Brand/Trademark owner directly.



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <https://www.sgs.com/en/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 83071443, or email: CN.Doccheck@sgs.com

SGS-CSTC Standards Technical Services (Shanghai) Co., Ltd.
Softline Laboratory

3rd Building, No. 889, Yishan Road, Xuhui District Shanghai, China 200233
中国·上海·徐汇区宜山路889号3号楼 邮编: 200233

t (86-21) 61402666
t (86-21) 61402666

f (86-21) 64958763
f (86-21) 64958763

www.sgsgroup.com.cn
sgs.china@sgs.com

Test Result

Tensile Strength

(ASTM D5034-21; Grab method)

As Received

-	Unit	A
MD	lbf	19.0
CD	lbf	14.4

Tearing Strength

(ASTM D5733-99)

-	Unit	A
MD	lbf	10.9
CD	lbf	4.9

Water Resistance(Hydrostatic Head)

(AATCC TM127-2017(2018)e; Hydrostatic Head; Rate of increase of water pressure: 60 mbar/min, temp. of distilled water: 21°C, Face Side Facing Water)

A(fabric)

<u>As Received</u>	No. 1	No. 2	No. 3	Average
Water Column(inH ₂ O)	>50.0	>50.0	>50.0	>50.0

Fabric Thickness

(ASTM D1777-96(Reapproved 2019))

-	Unit	A
Thickness	mm	0.18

Fabric Weight

(ASTM D3776/D3776M-20, Option C)

As Received

-	Unit	A
Weight	oz/yd ²	1.47
Weight	g/m ²	50.0



Surface Resistivity

Test Method: ASTM D257-14 (2021)^{ε1}

Test Condition:

Precondition: (23±2) °C, (50±5) %RH, 48 h

Electrode diameter: D₁=76 mm, D₂=88 mm

Test voltage: 500 Vdc

Test duration: 1 min

Lab Environmental: (23±2) °C, (50±5) %RH

Test Side: Back side

Test Result:

Specimen No.	Surface Resistance R _s (Ω)	Surface Resistivity ρ _s (Ω/sq)
1	9.82×10 ¹¹	4.21×10 ¹³
2	1.07×10 ¹²	4.59×10 ¹³
3	2.43×10 ¹²	1.04×10 ¹⁴
4	1.53×10 ¹²	6.57×10 ¹³
5	5.04×10 ¹¹	2.16×10 ¹³
Average	1.30×10 ¹²	5.59×10 ¹³

Note: Test specimens were cut from the sample.



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <https://www.sgs.com/en/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CSTC (Shanghai) Technical Service (Shanghai) Co., Ltd.
Softline Laboratory

3rd Building, No. 889, Yishan Road, Xuhui District Shanghai, China 200233
中国·上海·徐汇区宜山路889号3号楼 邮编: 200233

t (86-21) 61402666
t (86-21) 61402666

f (86-21) 64958763
f (86-21) 64958763

www.sgsgroup.com.cn
sgs.china@sgs.com

Sample Photo



Product information is provided by applicant without verification or authentication of the brand.

End of Report

Scan to see the report



SL52505272948001TX

Verification:
check.sgsonline.com.cn



SGS-CTC (China) Technical Service (Shanghai) Co., Ltd.
Softline Laboratory

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <https://www.sgs.com/en/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

3rd Building, No. 889, Yishan Road, Xuhui District Shanghai, China 200233
中国·上海·徐汇区宜山路889号3号楼 邮编: 200233

t (86-21) 61402666
t (86-21) 61402666

f (86-21) 64958763
f (86-21) 64958763

www.sgsgroup.com.cn
sgs.china@sgs.com